

Comparison of experimental data and theoretical calculations for electrical resistivity and Hall coefficient in $(\text{TMTSF})_2\text{PF}_6$

Victor M. Yakovenko^{a,1} and Anatoley T. Zheleznyak^b

^a*Department of Physics and Center for Superconductivity Research, University of Maryland, College Park, MD 20742, USA*

^b*MetricVision, a Thermo Electron Company, 8500 Cinder Bed Road, Suite 150, Newington, VA 22122, USA*

Abstract

The temperature dependences of the Hall coefficient and electrical resistivity recently measured by Moser *et al.* [Phys. Rev. Lett. **84**, 2674 (2000)] in the quasi-one-dimensional organic conductor $(\text{TMTSF})_2\text{PF}_6$ are quantitatively compared with our previous theoretical calculations [Synth. Met. **103**, 2202 (1999); Eur. Phys. J. B **11**, 385 (1999)]. We find a good agreement, albeit not with a fully consistent set of parameters for the two quantities.

Key words: Many-body and quasiparticle theories, Transport measurements, conductivity, Hall effect, magnetotransport, Organic conductors based on radical cation and/or anion salts, Organic superconductors

Recently, the temperature dependences of the Hall coefficient, as well as electrical resistivity, were measured in the quasi-one-dimensional (Q1D) organic conductor $(\text{TMTSF})_2\text{PF}_6$ by the two groups [1,2]. The results were interpreted using the Luttinger liquid concept in Ref. [1] and the conventional Fermi liquid theory in Ref. [2]. Before the experimental data became known, we had published theoretical calculations of the temperature dependences of the Hall coefficient [3] and electrical resistivity [4]. In the present paper, we quantitatively compare our theoretical predictions and the experimental results. Since we have calculated the Hall coefficient in the (a-b) plane, we compare only with the results of Ref. [1], where the Hall coefficient was measured in that geometry, unlike in Ref. [2], where the (b-c) plane geometry was employed. Electrical resistivity, calculated in Ref. [4] for the direction along the chains, is compared only with the experimental results of Ref. [1], because they correspond to constant volume, unlike the constant-pressure results of Ref. [2].

The Hall coefficient $R_H = \sigma_{xy}/H\sigma_{xx}\sigma_{yy}$, where σ_{ij} are the components of the conductivity tensor and H is the magnetic field, is usually a constant, because, in a simple Drude model, $\sigma_{xy} \propto \tau^2$ and

$\sigma_{xx,yy} \propto \tau$, so the temperature-dependent relaxation time τ cancels out in R_H . However, the experiment [1] found that R_H in $(\text{TMTSF})_2\text{PF}_6$ does depend on temperature. The authors invoked the Luttinger liquid concept in order to explain this effect. However, it has been shown theoretically that R_H of weakly coupled one-dimensional Luttinger chains does not depend on frequency and temperature [5], because the power-law dependences of σ_{xy} and σ_{yy} cancel out.

The Hall coefficient may depend on temperature if the system has relaxation times with different temperature dependences. (See discussion [6] of the “cold spots” for the cuprate high-temperature superconductors, where R_H is also temperature-dependent.) In Ref. [7], we had calculated the distribution of the umklapp scattering rates over the Fermi surface of a Q1D conductor and found that at low temperatures “hot spots” develop with a different temperature dependence. Using this distribution, we have calculated the temperature dependence of R_H in Ref. [3]. Fig. 1 shows our theoretical curve with the experimental points from Ref. [1]. In our calculation, the Hall coefficient consists of two terms: $R_H = R_H^{(0)} + R_H^{(1)}$. The first term is a temperature-independent band-structure contribution. In our fit, it is taken to be $R_H^{(0)} = 6.1 \times 10^{-9} \text{ m}^3/\text{C}$, which is 1.7 times greater than the value assumed in Ref. [1]. The second,

¹ Corresponding author. Phone: +1-301-405-6151, Fax: +1-301-314-9465, E-mail: yakovenk@physics.umd.edu, Web: <http://www2.physics.umd.edu/~yakovenk/>

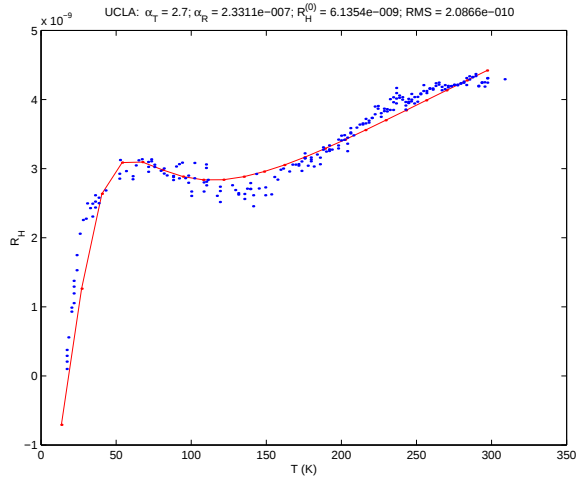


Fig. 1. Temperature dependence of the Hall coefficient R_H in the units of m^3/C . Experimental points are from Fig. 1 of Ref. [1] for the UCLA sample. The solid line is the theoretical curve (a) from Fig. 1 of Ref. [3].

temperature-dependent term $R_H^{(1)}$ is obtained by multiplying curve (a) of Fig. 1 from Ref. [3] by the factor $\alpha_R = 2.3 \times 10^{-7} m^3/C$. That corresponds to $p_F v_F / t_b = 38$, which is 0.57 of the value assumed in Ref. [3]. The temperature scale of Fig. 1 from Ref. [3] is increased by the factor $\alpha_T = 2.7$, which means that the transverse tunneling amplitudes t_b and t'_b are taken to be α_T times greater than the values 300 K and 30 K assumed in Ref. [3]. Line (a) in Fig. 1 of Ref. [3] corresponds to the phases $\varphi = \varphi' = 0$ in the transverse electron dispersion law (see the definitions in Ref. [3]). The other curves shown in Fig. 1 of Ref. [3] for different values of the phases qualitatively disagree with the experimental behavior [1].

In Ref. [4] we have calculated the temperature dependence of electrical resistivity R_{xx} along the chains by taking into account renormalization of umklapp scattering. Fig. 2 shows our theoretical curve with the experimental points from Ref. [1]. The theoretical line is taken from Fig. 4 of Ref. [4] with the parameters $\varphi = \pi/4$, $\varphi' = 2\varphi$, $t_b = 290$ K, $t'_b = 20$ K, and the temperature scale is increased by the factor $\alpha_T = 1.3$. The vertical scale of Fig. 4 of Ref. [4] is multiplied by the factor $\alpha_R = 0.23$.

Overall, the theory correctly captures the experimental features. However, the sets of model parameters utilized to obtain the fits in Figs. 1 and 2 are not the same. First, the values of the phases φ and φ' are different. The Hall coefficient is very sensitive to the choice of φ and φ' , and a sensible fit is possible only when the phases are zero or close to zero. On the other hand, R_{xx} is less sensitive to the choice of the phases. If the phases are zero, the main problem is the upturn of R_{xx} when temperature approaches to the SDW transition temper-

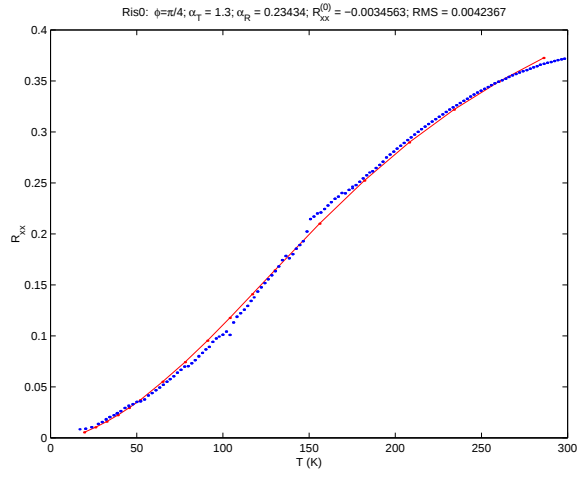


Fig. 2. Temperature dependence of electrical resistivity along the chains. Experimental points are from Fig. 2 of Ref. [1] for the Risø sample. The solid line is the theoretical curve with $\varphi = \pi/4$ and $t'_b = 20$ K from Fig. 4 of Ref. [4].

ature (see Fig. 4 of Ref. [4]). The upturn can be suppressed by selecting a small but finite value for the phases (see the other curves in Fig. 4 of Ref. [4]) or by selecting a greater value for t'_b (see Fig. 6 of Ref. [4]). The second problem is the difference in the temperature scales α_T utilized to obtain the fits in Figs. 1 and 2. While the scale 1.3 for R_{xx} is reasonable, the value 2.7 for R_H is too big. However, the scale of R_H is controlled primarily by t'_b (because $R_H^{(1)} = 0$ if $t'_b = 0$ [3]), whereas the scale of R_{xx} is controlled by t_b . So the agreement could be achieved by increasing t'_b without increasing t_b . The increase of t'_b could suppress the SDW transition, which is present at the ambient pressure, but that could be compensated by an increase in the interaction strength.

The space of model parameters is big, and there are opportunities to achieve better agreement with the experiment by optimizing the choice of parameters. Our first try presented here appears to be promising.

References

- [1] J. Moser, J. R. Cooper, D. Jérôme, B. Alavi, S. E. Brown, and K. Bechgaard, Phys. Rev. Lett. **84**, 2674 (2000).
- [2] G. Mihály, I. Kézsmárki, F. Zámboorszky, and L. Forró, Phys. Rev. Lett. **84**, 2670 (2000).
- [3] V. M. Yakovenko and A. T. Zheleznyak, Synth. Met. **103**, 2202 (1999).
- [4] A. T. Zheleznyak and V. M. Yakovenko, Eur. Phys. J. B **11**, 385 (1999).
- [5] A. V. Lopatin, Phys. Rev. B **57**, 6342 (1998); A. Lopatin, A. Georges, and T. Giamarchi, cond-mat/0008066.
- [6] A. T. Zheleznyak, V. M. Yakovenko, H. D. Drew, and I. Mazin, Phys. Rev. B **57**, 3089 (1998); **59**, 207 (1999).
- [7] A. T. Zheleznyak and V. M. Yakovenko, Synth. Met. **70**, 1005 (1995).